

Battery Pack Test Report ***(Package Drop & UN38.3)***

Customer: Lenovo

Pack Model: L17C4PB1

Nominal voltage: 15.36V

Nominal capacity: 5185mAh/79Wh

Configuration: 4S1P

Customer P/N: 5B10P35084

Celxpert P/N: 921300141

Cell Type: Coslight CA3367E0G 5185mAh

Jan. 23 . 2018

Approved by _____

Reviewed by _____

Prepared by _____

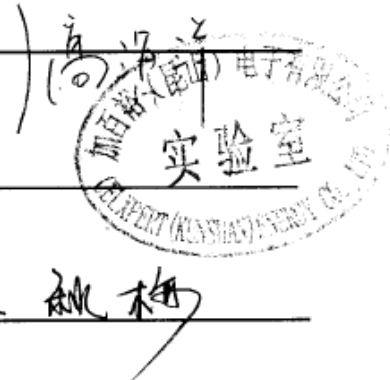


Figure photo of the pack



<p>Lenovo</p> <p>Lenovo is the trademark of Lenovo, used under license. Lenovo 是联想集团所属企业的商标，根据许可使用。</p> <p>Rechargeable Li-Ion Battery (锂离子电池组) Model name (型号/型号): L17C4PB1 Manufactured By Celxpert(Kunshan)Energy Co., Ltd. Cell made in China / Pack processed in China 制造商：加百裕工业股份有限公司 制造地 / 製造地：中国 / 中國</p>	<p>EU contact: Lenovo, Einsteinova21, 85101 Bratislava, Slovakia For use with Lenovo laptops, tablets and convertibles. PLEASE REFER TO USER MANUAL OR FOLLOW LOCAL ORDINANCES AND/OR REGULATIONS FOR DISPOSAL 请参考使用说明或者遵循相关法律规定处理废弃电池 Rating: 15.36V --- TYP 5185mAh/79Wh MIN 5030mAh/77Wh 額定容量：5030mAh, 充电限制电压：17.6V</p> <div style="display: flex; justify-content: space-between; align-items: center;"> <div style="border: 1px solid black; padding: 5px; text-align: center;"> <p>PS E</p> <p>15.36V 5030mAh レノボ・ジャパン株式会社</p> </div> <div style="text-align: right;"> <p>TIS 2217-2548 Lenovo (Thailand) Limited 4ICP4/67/141</p> </div> </div>
--	--

PS:此報告僅針對送檢樣品有效

The test report is valid for the tested samples only.

1. UN38.3 Test Report

Test Period	2017/05/16~2017/06/08		Test Spec.	ST/SG/AC.10/11/Rev.5 Amend.1&2	
Parts Name	Battery Pack	Application	NB	Quantity	Pack 16PCS/Cell 25pcs

1.1 Test Summary

Item	Test Item	Test Result	Details
T1	Altitude simulation test (UN38.3-1)	Pass	Page 9
T2	Thermal test (UN38.3-2)	Pass	Page 10
T3	Vibration test (UN38.3-3)	Pass	Page 11
T4	Shock test (UN38.3-4)	Pass	Page 12
T5	Short Circuit test (UN38.3-5)	Pass	Page 13
T6	Crush Test (UN38.3-6)	Pass	Page 13
T7	Overcharge test (UN38.3-7)	Pass	Page 14
T8	Forced discharge test (UN38.3-8)	Pass	Page 15

The battery pack passes UN38.3 test.

1.2 Test sample list

No.	Pack S/N	Test item	No.	Cell Num.	Test item
1	Sample No:1/16	38.3.1~5	1	Coslight CA3367E0G 5185mAh	38.3.6
2	Sample No:2/16	38.3.1~5	2	Coslight CA3367E0G 5185mAh	38.3.6
3	Sample No:3/16	38.3.1~5	3	Coslight CA3367E0G 5185mAh	38.3.6
4	Sample No:4/16	38.3.1~5	4	Coslight CA3367E0G 5185mAh	38.3.6
5	Sample No:5/16	38.3.1~5	5	Coslight CA3367E0G 5185mAh	38.3.6
6	Sample No:6/16	38.3.1~5	6	Coslight CA3367E0G 5185mAh	38.3.8
7	Sample No:7/16	38.3.1~5	7	Coslight CA3367E0G 5185mAh	38.3.8
8	Sample No:8/16	38.3.1~5	8	Coslight CA3367E0G 5185mAh	38.3.8
9	Sample No:9/16	38.3.7	9	Coslight CA3367E0G 5185mAh	38.3.8
10	Sample No:10/16	38.3.7	10	Coslight CA3367E0G 5185mAh	38.3.8
11	Sample No:11/16	38.3.7	11	Coslight CA3367E0G 5185mAh	38.3.8
12	Sample No:12/16	38.3.7	12	Coslight CA3367E0G 5185mAh	38.3.8
13	Sample No:13/16	38.3.7	13	Coslight CA3367E0G 5185mAh	38.3.8
14	Sample No:14/16	38.3.7	14	Coslight CA3367E0G 5185mAh	38.3.8
15	Sample No:15/16	38.3.7	15	Coslight CA3367E0G 5185mAh	38.3.8
16	Sample No:16/16	38.3.7	16	Coslight CA3367E0G 5185mAh	38.3.8
			17	Coslight CA3367E0G 5185mAh	38.3.8
			18	Coslight CA3367E0G 5185mAh	38.3.8
			19	Coslight CA3367E0G 5185mAh	38.3.8
			20	Coslight CA3367E0G 5185mAh	38.3.8
			21	Coslight CA3367E0G 5185mAh	38.3.8
			22	Coslight CA3367E0G 5185mAh	38.3.8
			23	Coslight CA3367E0G 5185mAh	38.3.8
			24	Coslight CA3367E0G 5185mAh	38.3.8
			25	Coslight CA3367E0G 5185mAh	38.3.8

1.3 Test result

Item	Test Item	Test specification	Judge criteria	Sample(s)				
T1	Altitude Simulation (UN38.3-1)	1-1. 4 batteries are standard charged. 4 batteries are 1C cycled 50 times, ending in fully charged state. All batteries weight is measured. The charged batteries voltage are measured and recorded. 1-2. Batteries shall be stored at a pressure of 11.6Kpa or less for at least six hours at ambient temperature 20+/-5 °C. 1-3. Vacuum is released. All cells weight is measured. The charged cell voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)				
Test Period	Start: 2017/05/16 End:2017/05/16							
Test Equipment	數位電表 Q153, 電子天平 Q090, 真空烘箱 Q146							
Major Problem	-							
Warning Point	-							
Recommendation	The battery packs pass the test.							
Raw Data	Altitude Simulation Test on Charged Packs							
	No.	Before		After		voltage residue	mass loss	other event
		OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
	1	16.953	315.27	16.941	315.25	99.93%	0.01%	O
	2	16.974	315.29	16.963	315.26	99.94%	0.01%	O
	3	16.966	315.24	16.955	315.22	99.94%	0.01%	O
	4	16.967	315.34	16.954	315.32	99.92%	0.01%	O
	5	16.754	315.24	16.742	315.22	99.93%	0.01%	O
	6	16.833	315.23	16.820	315.21	99.92%	0.01%	O
	7	16.789	315.19	16.778	315.17	99.93%	0.01%	O
8	16.712	315.28	16.698	315.25	99.92%	0.01%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								

Item	Test Item	Test specification	Judge criteria	Sample(s)					
T2	Thermal test (UN38.3-2)	2-1. Packs are stored for 6 hours at 72±2°C, followed by storage for 6 hours at -40±2°C. The maximum time interval between test temperature extremes is 30 minutes. 2-2.Repeat 2-1 for 10 times. Then store the packs at ambient for 24 hours. All packs weight are measured. The charged battery voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)					
Test Period		Start: 2017/05/17 End:2017/05/22							
Test Equipment		數位電表 Q153, 電子天平 Q090, 冷熱衝擊機 Q336							
Major Problem		-							
Warning Point		-							
Recommendation		The packs pass the test.							
Raw Data		Thermal Test on Charged Packs							
		No.	Before		After		voltage residue	mass loss	other event
			OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
		1	16.941	315.25	16.872	315.21	99.59%	0.01%	O
		2	16.963	315.26	16.887	315.22	99.55%	0.01%	O
		3	16.955	315.22	16.880	315.19	99.56%	0.01%	O
		4	16.954	315.32	16.880	315.29	99.56%	0.01%	O
		5	16.742	315.22	16.671	315.17	99.58%	0.01%	O
		6	16.820	315.21	16.745	315.17	99.55%	0.01%	O
		7	16.778	315.17	16.710	315.13	99.59%	0.01%	O
8	16.698	315.25	16.623	315.21	99.55%	0.01%	O		
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire									
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire									

Item	Test Item	Test specification	Judge criteria	Sample(s)				
T3	Vibration test (UN38.3-3)	3-1. Packs are firmly secured to the platform of the vibration machine without distorting the packs in such a manner as to faithfully transmit the vibration. The vibration shall be a sinusoidal waveform with a logarithmic sweep between 7 and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle shall be repeated 12 times for a total of 3 hours for each of 3 mutually perpendicular to the terminal face. 3-2. The logarithmic frequency sweep is as follows: 7-18 Hz → 1gn 18-50 Hz → 0.8mm amplitude 50-200 Hz → 8gn 3-3. All packs weight are measured. The charged packs voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)				
Test Period	Start: 2017/05/26 End:2017/05/29							
Test Equipment	數位電表 Q153, 電子天平 Q090, 振動測試機 Q300							
Major Problem	-							
Warning Point	-							
Recommendation	The packs pass the test.							
Raw Data	Vibration Test on Charged Packs							
	No.	Before		After		voltage residue	mass loss	other event
		OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
	1	16.872	315.21	16.865	315.18	99.96%	0.01%	O
	2	16.887	315.22	16.880	315.19	99.96%	0.01%	O
	3	16.880	315.19	16.872	315.16	99.95%	0.01%	O
	4	16.880	315.29	16.872	315.27	99.95%	0.01%	O
	5	16.671	315.17	16.663	315.15	99.95%	0.01%	O
	6	16.745	315.17	16.739	315.14	99.96%	0.01%	O
	7	16.710	315.13	16.701	315.10	99.95%	0.01%	O
8	16.623	315.21	16.616	315.19	99.96%	0.01%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								

Item	Test Item	Test specification	Judge criteria	Sample(s)					
T4	Shock test (UN38.3-4)	4-1. Packs shall be secured to the testing machine by means of a rigid mount, which will support all mounting surfaces. 4-2. Packs shall be subjected to a half-sine shock of peak acceleration 150gn and pulse duration of 6 milliseconds. Each pack shall be subjected to 3 shocks in the positive direction followed by three shocks in the negative direction of three mutually perpendicularly mounting positions of the pack for a total of 18 shocks. 4-3. All batteries weight are measured. The charged cell voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)					
Test Period		Start: 2017/06/05 End:2017/06/05							
Test Equipment		數位電表 Q153, 電子天平 Q090, 衝擊測試機 Q154							
Major Problem		-							
Warning Point		-							
Recommendation		The packs pass the test.							
Raw Data		Shock Test on Charged Packs							
		No.	Before		After		voltage residue	mass loss	other event
			OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
		1	16.865	315.18	16.852	315.17	99.92%	0.00%	O
		2	16.880	315.19	16.865	315.18	99.91%	0.01%	O
		3	16.872	315.16	16.861	315.15	99.93%	0.01%	O
		4	16.872	315.27	16.862	315.25	99.94%	0.01%	O
		5	16.663	315.15	16.649	315.13	99.92%	0.01%	O
		6	16.739	315.14	16.726	315.12	99.92%	0.01%	O
		7	16.701	315.10	16.686	315.08	99.91%	0.01%	O
8	16.616	315.19	16.605	315.17	99.93%	0.01%	O		
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire									
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire									

Item	Test Item	Test specification	Judge criteria	Sample(s)																														
T5	Short Circuit Test (UN38.3-5)	5-1.Packs are placed in to a 55±2°C oven, and exterior packs temperature are monitored 5-2.When packs exterior reach 55±2°C, they are shorted by connecting terminals with a copper wire of resistance less than 100m Ohm. 5-4. The short was continued for more than 1hour or the cell temperature return to 55°C. The packs are observed for a further 6 hours.	No rupture, no disassembly, no explosion, no fire, no smoke. Packs exterior peak temperature <170°C.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)																														
Test Period		Start: 2017/06/06 End:2017/06/08																																
Test Equipment		數位電表 Q153, 資料收集器 Q075, 烘箱 Q171																																
Recommendation		The packs pass the test.																																
Raw Data		<table border="1"> <thead> <tr> <th colspan="3">Short Circuit Test on Charged Packs</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>1</td><td>54.63</td><td>O</td></tr> <tr><td>2</td><td>55.27</td><td>O</td></tr> <tr><td>3</td><td>55.49</td><td>O</td></tr> <tr><td>4</td><td>55.43</td><td>O</td></tr> <tr><td>5</td><td>56.73</td><td>O</td></tr> <tr><td>6</td><td>54.86</td><td>O</td></tr> <tr><td>7</td><td>56.91</td><td>O</td></tr> <tr><td>8</td><td>54.82</td><td>O</td></tr> </tbody> </table> <p>Note: D-Disassembly ; R-Rupture ; F-Fire O- No Disassembly , No Rupture , No Fire</p>			Short Circuit Test on Charged Packs			No.	Max. Temp.(°C)	Other event	1	54.63	O	2	55.27	O	3	55.49	O	4	55.43	O	5	56.73	O	6	54.86	O	7	56.91	O	8	54.82	O
Short Circuit Test on Charged Packs																																		
No.	Max. Temp.(°C)	Other event																																
1	54.63	O																																
2	55.27	O																																
3	55.49	O																																
4	55.43	O																																
5	56.73	O																																
6	54.86	O																																
7	56.91	O																																
8	54.82	O																																
Item	Test Item	Test specification	Judge criteria	Sample(s)																														
T6	Crush test/ Impact test (UN38.3-6)	6-1.Cell's diameter > 20mm, Execution impact test. (A 9.1 Kg mass is to be dropped from a height of 61±2.5cm onto the sample.) 6-2.Cell's diameter < 20mm, Execution crush test (The cells are crushed with a 13 KN with the crush tester. Once the force is obtained it is to be released.)	External temperature of cell does not exceed 170°C and there is no disassembly and no fire within 6 hours of the test.	5 cells are 50% charged (Cell #1~5)																														
Test Period		Start: 2017/05/17 End: 2017/05/18																																
Test Equipment		數位電表 Q153, 資料收集器 Q152, 擠壓試驗機 Q437/撞擊測試機 Q231																																
Recommendation		The Cells pass the test.																																
Raw Data		<table border="1"> <thead> <tr> <th colspan="3">Crush Test on 50% Charged Cells</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>1</td><td>21.36</td><td>O</td></tr> <tr><td>2</td><td>20.56</td><td>O</td></tr> <tr><td>3</td><td>21.43</td><td>O</td></tr> <tr><td>4</td><td>22.16</td><td>O</td></tr> <tr><td>5</td><td>21.49</td><td>O</td></tr> </tbody> </table> <p>Note: D-Disassembly ; F-Fire / O-No Disassembly , No Fire</p>			Crush Test on 50% Charged Cells			No.	Max. Temp.(°C)	Other event	1	21.36	O	2	20.56	O	3	21.43	O	4	22.16	O	5	21.49	O									
Crush Test on 50% Charged Cells																																		
No.	Max. Temp.(°C)	Other event																																
1	21.36	O																																
2	20.56	O																																
3	21.43	O																																
4	22.16	O																																
5	21.49	O																																

Item	Test Item	Test specification	Judge criteria	Sample(s)
T7	Overcharge test (UN38.3-7)	7-1. The charge current shall be twice the Spec's recommended maximum continuous charge current. 7-2. The minimum voltage of the test shall be as follows: (a) When the Spec's recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage of the battery or 22V. (b) When the Spec's recommended charge voltage is more than 18V, the minimum voltage of the test shall be 1.2 times the maximum charge voltage. 7-3. Tests are to be conducted at ambient temperature. The duration of the test shall be 24 hours.	No disassembly, no fire within seven days after the test.	4 packs are fully charged (Pack#9~12) 4 packs are 50 times cycled ending in fully charged state (Pack #13~16)
Test Period		Start: 2017/05/24 End: 2017/05/28		
Test Equipment		數位電表 Q153, 資料收集器 Q078, 電源供應器 Q148/Q149/Q150		
Major Problem		-		
Warning Point		-		
Recommendation		The packs pass the test.		
Raw Data	Overcharge Test on Charged Packs			
	No.	Charge Voltage(V)	Charge Current(A)	Max. Temp.(°C)
	9	22.0 V	6.8	20.36
	10			21.56
	11			22.49
	12			21.59
	13			21.35
	14			20.87
	15			20.46
	16			21.49
Note: D-Disassembly ; F-Fire / O-No Disassembly ,No Fire				

Item	Test Item	Test specification	Judge criteria	Sample(s)																																																																									
T8	Forced discharge test (UN38.3-8)	Cell shall be forced discharged at ambient temperature by connecting it in series with a 12 V D.C. power supply at an initial current equal to the maximum discharge current Specified by the manufacturer.	No disassembly, no fire within seven days after the test.	10 cells are first cycle in fully discharged states (Pack#6~15) 10 cells are after 50 cycles ending in fully discharged states (Pack #16~25)																																																																									
Test Period	Start: 2017/05/29 End:2017/06/01																																																																												
Test Equipment	數位電表 Q153, 資料收集器 Q160, 電源供應器 Q147/Q236/Q237																																																																												
Major Problem	-																																																																												
Warning Point	-																																																																												
Recommendation	The packs pass the test.																																																																												
Raw Data	<table border="1"> <thead> <tr> <th colspan="3">Forced discharge are first cycle in fully discharged</th> <th colspan="3">Forced discharge are after 50 cycles ending in fully discharged</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>6</td><td>35.46</td><td>O</td><td>16</td><td>27.59</td><td>O</td></tr> <tr><td>7</td><td>26.59</td><td>O</td><td>17</td><td>29.65</td><td>O</td></tr> <tr><td>8</td><td>24.76</td><td>O</td><td>18</td><td>31.26</td><td>O</td></tr> <tr><td>9</td><td>31.46</td><td>O</td><td>19</td><td>32.59</td><td>O</td></tr> <tr><td>10</td><td>32.56</td><td>O</td><td>20</td><td>26.58</td><td>O</td></tr> <tr><td>11</td><td>26.59</td><td>O</td><td>21</td><td>24.79</td><td>O</td></tr> <tr><td>12</td><td>24.78</td><td>O</td><td>22</td><td>26.59</td><td>O</td></tr> <tr><td>13</td><td>26.59</td><td>O</td><td>23</td><td>36.59</td><td>O</td></tr> <tr><td>14</td><td>24.69</td><td>O</td><td>24</td><td>34.79</td><td>O</td></tr> <tr><td>15</td><td>29.56</td><td>O</td><td>25</td><td>37.13</td><td>O</td></tr> </tbody> </table>					Forced discharge are first cycle in fully discharged			Forced discharge are after 50 cycles ending in fully discharged			No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event	6	35.46	O	16	27.59	O	7	26.59	O	17	29.65	O	8	24.76	O	18	31.26	O	9	31.46	O	19	32.59	O	10	32.56	O	20	26.58	O	11	26.59	O	21	24.79	O	12	24.78	O	22	26.59	O	13	26.59	O	23	36.59	O	14	24.69	O	24	34.79	O	15	29.56	O	25	37.13	O
	Forced discharge are first cycle in fully discharged			Forced discharge are after 50 cycles ending in fully discharged																																																																									
	No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event																																																																							
	6	35.46	O	16	27.59	O																																																																							
	7	26.59	O	17	29.65	O																																																																							
	8	24.76	O	18	31.26	O																																																																							
	9	31.46	O	19	32.59	O																																																																							
	10	32.56	O	20	26.58	O																																																																							
	11	26.59	O	21	24.79	O																																																																							
	12	24.78	O	22	26.59	O																																																																							
	13	26.59	O	23	36.59	O																																																																							
	14	24.69	O	24	34.79	O																																																																							
	15	29.56	O	25	37.13	O																																																																							
	Note:D-Disassembly ; F-Fire / O-No Disassembly , No Fire																																																																												