

### **Declaration**

We, LG Chem, Ltd. hereby declares, that the product

Product Name : Rechargeable Li-ion Battery Pack Regulatory Model Number : SB10K97592

Based on the request of SRICI, LG Chem, Ltd. submits a letter of authorization regarding below changes have no impact on UN38.3 test report. LG Chem, Ltd. confirms all specifications are identical except for below changes.



Date: July 19<sup>th</sup>, 2016

(guing

Name / Title: Dae Ho Nam / Senior Manager

문서번호	QAE-E	F02-15821-PKLBP7221E
Prepared	남익현	the
	장승현	
Reviewed	남대호	any
	박광민	$\mathcal{O}$
Approved	김병수	36

SolutionPartner

## UN Test Report - SB10J78997 (Nom.42Wh, 11.4V)-

### 목 차

1. UN Transportation Regulation Test

2. Test Procedure

3. Test Result

4. Sample Image

Appendix. Drop Test Report

2015. 08. 21



# **1. UN Transportation Regulation Test**


Test	Condition	Requirements	
Test 1. Altitude Simulation	Storing at (low pressure)11.6kPa for 6hr at 20+/-5℃	- Measuring mass before/	
Test 2. Thermal Test	[72±2℃,6hr ↔ -40±2℃,6hr,interval max. 30min] x 10cycle Storing at 20±5℃ for 24h	after each test (If M<1g, less than 0.5%, If 1g≤M≤75g, less than 0.2%, If	
Test 3. Vibration	[7Hz↔200Hz↔7Hz, in 15min] x 12 times x 3 direction 1) sinusoidal waveform with a logarithmic sweep 2) 7Hz 18Hz (maintaining 1gn) app. 50Hz (until 8gn) 200Hz (maintaining 8gn), 1.6mm total excursion	M>75g, less than 0.1%) - Measuring voltage before/ after each test (more than 90%) - No leakage, no venting,	
Test 4. Shock	Half sine shock (peak acceleration : 150gn, pulse duration : 6msec) x 6 ( $\pm$ x, y, z), direction x 3 cycle	no disassembly, no rupture, no fire	
Test 5. External Short Circuit	100mΩ ext. short-circuit at 55±2℃ 1hr continue after returning at 55±2℃	- No disassembly, no rupture, no fire within 6 hours after the test - Temp. monitoring (max. 170℃)	
Test 6. Impact for cylindrical cells ( > 18mm diameter)	Φ=15.8mm bar, 9.1kg mass, 61±2.5cm height	- No disassembly,	
Test 6. Crush for cylindrical cells ( ≤ 18mm diameter) for prismatic, pouch, coin/button cells	Crushing rate :1.5cm/s, until 13kN $\pm$ 0.78kN or 100mV drop or 50% deformation	no fire within 6 hours after the test - Temp. monitoring (max. 170℃)	
Test 7. Overcharge	Current = Manufacturer's recommended max. continuous charge current X 2 Voltage 1.If charge voltage ≤ 18V, V (min.) = 2 x (max. charge voltage) or V (min.) = 22V. 2.If charge voltage > 18V, V (min.) = 1.2 x (max. charge voltage)	- No disassembly, no fire within 7 days after the test	
Test 8. Forced Discharge	Discharge at max. discharge current (with 12V DC power supply), Duration time = rated capacity/initial test current		

\* Tests through T1-T5 shall be conducted in sequence with the same samples.

\* We declare that the above-mentioned test is the result of being checked according to UN Test

(Manual of Test and Criteria ST/SG/AC.10/11/Rev.5/Amd.2)

## 2. Test Procedure

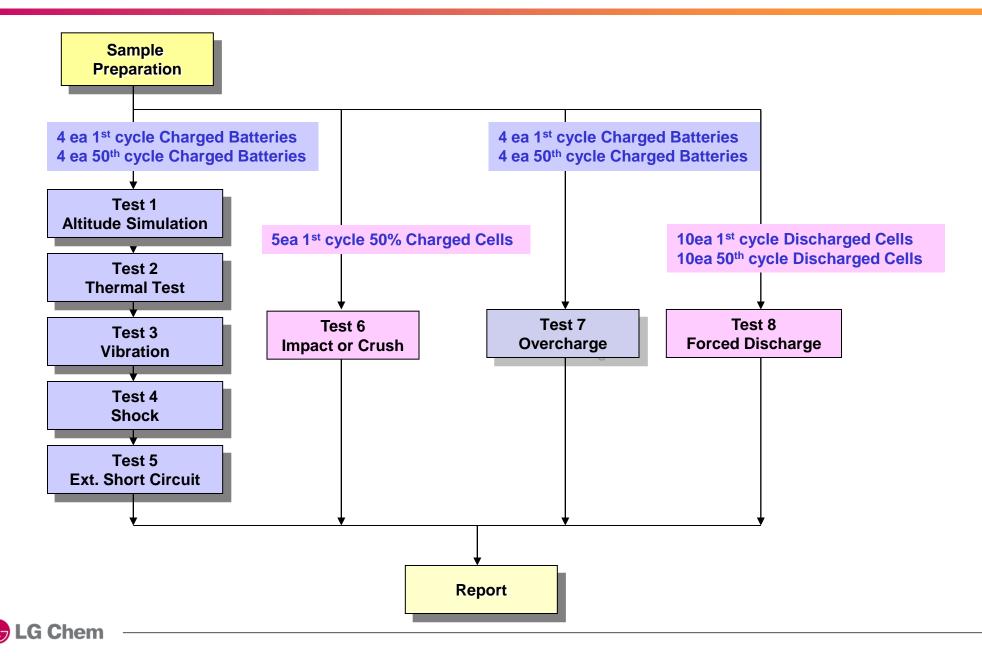

# 3-1. T1-T4 Test Result

Before Altitude (T1)				Thermal (T2)				Vibration (T3)				Shock (T4)											
	NO.	OCV	Mass	OCV		Residual OCV(%)		Result	OCV		Residual OCV(%)		Result	OCV		Residual OCV(%)		Result	OCV		Residual OCV(%)		Result

A. 1st cycle fully charged state

	1	12.696	189.95	12.691	189.95	99.96	0.000	Pass	12.530	189.94	98.73	0.005	Pass	12.524	189.94	99.95	0.000	Pass	12.520	189.93	99.97	0.005	Pass
	2	12.690	189.97	12.689	189.97	99.99	0.000	Pass	12.534	189.95	98.78	0.011	Pass	12.531	189.94	99.98	0.005	Pass	12.527	189.94	99.97	0.000	Pass
Charge	3	12.694	189.95	12.688	189.94	99.95	0.005	Pass	12.522	189.92	98.69	0.011	Pass	12.518	189.90	99.97	0.011	Pass	12.517	189.89	99.99	0.005	Pass
	4	12.692	189.98	12.692	189.98	100.00	0.000	Pass	12.522	189.97	98.66	0.005	Pass	12.517	189.96	99.96	0.005	Pass	12.512	189.96	99.96	0.000	Pass
	Ave.	12.693	189.96	12.690	189.96	99.98	0.001	-	12.527	189.95	98.72	0.008	-	12.523	189.94	99.96	0.005	-	12.519	189.93	99.97	0.003	-

### B. 50th cycle fully charged state

	5	12.680	189.97	12.676	189.97	99.97	0.000	Pass	12.507	189.97	98.67	0.000	Pass	12.504	189.95	99.98	0.011	Pass	12.501	189.94	99.98	0.005	Pass
	6	12.671	189.96	12.665	189.94	99.95	0.011	Pass	12.513	189.93	98.80	0.005	Pass	12.507	189.91	99.95	0.011	Pass	12.506	189.90	99.99	0.005	Pass
Charge	7	12.698	189.93	12.695	189.92	99.98	0.005	Pass	12.544	189.90	98.81	0.011	Pass	12.540	189.89	99.97	0.005	Pass	12.537	189.89	99.98	0.000	Pass
	8	12.678	189.92	12.673	189.92	99.96	0.000	Pass	12.502	189.91	98.65	0.005	Pass	12.498	189.89	99.97	0.011	Pass	12.492	189.88	99.95	0.005	Pass
	Ave.	12.682	189.95	12.677	189.94	99.96	0.004	-	12.517	189.93	98.73	0.005	-	12.512	189.91	99.97	0.009	-	12.509	189.90	99.97	0.004	-

Requirement	<ul> <li>Measuring mass before/after each test (If M&gt;75g, less than 0.1%, 1g≤M≤75, less than 0.2%, M&lt;1g, less than 0.5%)</li> <li>Measuring voltage before/after each test (more than 90%, only charged samples)</li> <li>No leakage, no venting, no disassembly, no rupture, no fire</li> </ul>
LG Chem	

# 3-2. T5/T7 Test Result

	EXT.Short Circuit (T5)										
	NO.	Initial OCV(V)	Max. Temp (℃)	Result							
A. 1st cyc	e fully charged stat	te									
	1	12.520	56.44	Pass							
	2	12.527	56.72	Pass							
Charge	3	12.517	56.53	Pass							
	4	12.512	57.00	Pass							
	MAX.	12.527	57.00	-							

Test Condition
- 100m $\Omega$ ext. short-circuit at 55 $\pm 2^\circ C$

		Over Charge (	<b>T7)</b>										
	NO.	Initial OCV(V)	Max. Temp (℃)	Result									
A. <u>1st cyc</u>	A. 1st cycle fully charged state												
	9	12.691	25.48	Pass									
	10	12.692	24.72	Pass									
Charge	11	12.691	26.09	Pass									
	12	12.691	25.85	Pass									
	MAX.	12.692	26.09	-									

### **Test Condition**

- Max. Charge Current : 3630mA

- CC/CV 2Imax(7260mA) 22V cut-off 24Hr

	E	<b>KT.Short Circu</b>	it (T5)										
	NO.	Initial OCV(V)	Max. Temp (℃)	Result									
B. <u>50th cy</u>	3. 50th cycle fully charged state												
	5	12.501	56.91	Pass									
	6	12.506	56.43	Pass									
Charge	7	12.537	56.60	Pass									
	8	12.492	56.89	Pass									
	MAX.	12.537	56.91	-									

Temperature ≤	170	(°C)	)

- No disassembly, no rupture, no fire within 6 hours after the test

Over Charge (T7)												
NO.	Initial OCV(V)	Max. Temp (℃)	Result									

Requirement

#### B. 50th cycle fully charged state

Charge	13	12.678	24.93	Pass
	14	12.675	24.35	Pass
	15	12.674	24.80	Pass
	16	12.674	25.81	Pass
	MAX.	12.678	25.81	-

### Requirement

- No disassembly, no fire within 7 day after the test



# 3-3. T6/T8 Test Result (ICP485490L1)

Crush (T6)							
Direction	NO.	Initial OCV(V)	Max. Temp (℃)	Result			
A. 1st cycle 50% charged state							
	C-1	3.849	23.44	Pass			
	C-2	3.853	23.49	Pass			
Flat	C-3	3.847	23.38	Pass			
	C-4	3.854	23.47	Pass			
	C-5	3.850	23.43	Pass			
MAX.		3.854	23.49	-			

Test Condition				
- Crushing rate :1.5cm/s, until 13kN $\pm$ 0.78kN or 100mV drop or 50% deformation				

Requirement
- Temperature ≤ 170 (°C)
- No disassembly, no fire within 6 hours after the test

	Forced Discharge (T8)					
NO.	Initial OCV(V)	Max. Temp (℃)	Result			
A. 1st cycle fully discharged state						
C-6	3.012	47.56	Pass			
C-7	3.007	46.43	Pass			
C-8	3.010	47.48	Pass			
C-9	3.011	48.55	Pass			
C-10	3.017	47.54	Pass			
C-11	3.011	47.30	Pass			
C-12	3.014	46.59	Pass			
C-13	3.009	45.37	Pass			
C-14	3.013	45.11	Pass			
C-15	3.012	47.08	Pass			
MAX.	3.017	48.55	-			
B. 50th cycle f	B. 50th cycle fully discharged state					
C-16	3.115	43.46	Pass			
C-17	3.117	46.52	Pass			
C-18	3.121	46.80	Pass			
C-19	3.130	43.24	Pass			
C-20	3.127	44.67	Pass			
C-21	3.113	47.32	Pass			
C-22	3.125	43.17	Pass			
C-23	3.118	44.28	Pass			
C-24	3.117	45.14	Pass			
C-25	3.124	44.30	Pass			
MAX.	3.130	47.32	-			

#### **Test Condition**

Discharge at max. discharge current (with 12V DC power supply) : 3630mA Duration time: rated capacity (60min)

### Requirement

- No disassembly, no fire within 7 days after the test



## 4. Sample Image





