

# ***Battery Pack Test Report*** ***(Package Drop & UN38.3)***

Customer: Lenovo

Pack Model: L17C3PG1

Nominal voltage: 11.4V

Nominal capacity: 4645mAh/52.5Wh

Configuration: 3S1P

Customer P/N: 5B10Q88561

Celxpert P/N: 921300185

Cell Type: Coslight CA595490HV 4645mAh

Dec. 08 . 2017

Approved by \_\_\_\_\_

Reviewed by \_\_\_\_\_

Prepared by \_\_\_\_\_

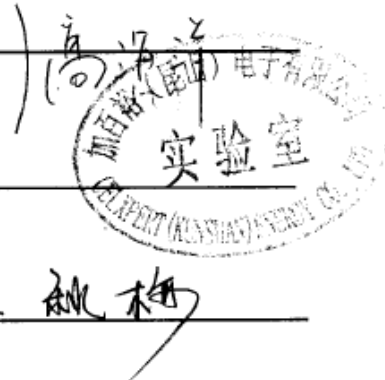


Figure photo of the pack



PS:此報告僅針對送檢樣品有效

The test report is valid for the tested samples only.

# 1. Package Drop Test Report

Test Period	2017/11/13		Test Spec.	IATA A58 & QS-3Q-043	
Sample Level	Mass Production	Sample Mode	Finished Product	Quantity	32 PCS

## 1.1 DECSRIPTION OF TEST EQUIPMENTS

Kingdom Technology KD-128AS drop tester. Description of performance:

Payload capacity: 160 lbs. (72.6 kg)

Payload dimensions: Length: 61 cm / Width: 76 cm / Height: 90cm

Drop height range: 30 - 180 cm

Base Plate Material: Solid Steel (Std.)

Base Plate Size: 76.2x114.3x1.3cm

## 1.2 TEST CONDITION

Drop height: 120cm

Drop weight: 8.167kg

Drop position: One corner, three edges and three faces with 1 time. (Total: 7 drops).

Drop Position and sequence: Ref. attachment 1

## 1.3 SUMMARY OF TEST

Concluding the follow check items, the result of the test is **pass**.


Check items	Before	After
Battery pack function	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail
Battery pack appearance	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail
Package internal status	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail
Package outside status	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail	<input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail

Test photographs please refer to Attachment 2

Function Check details please refer to Attachment 3

## Attachment 1:



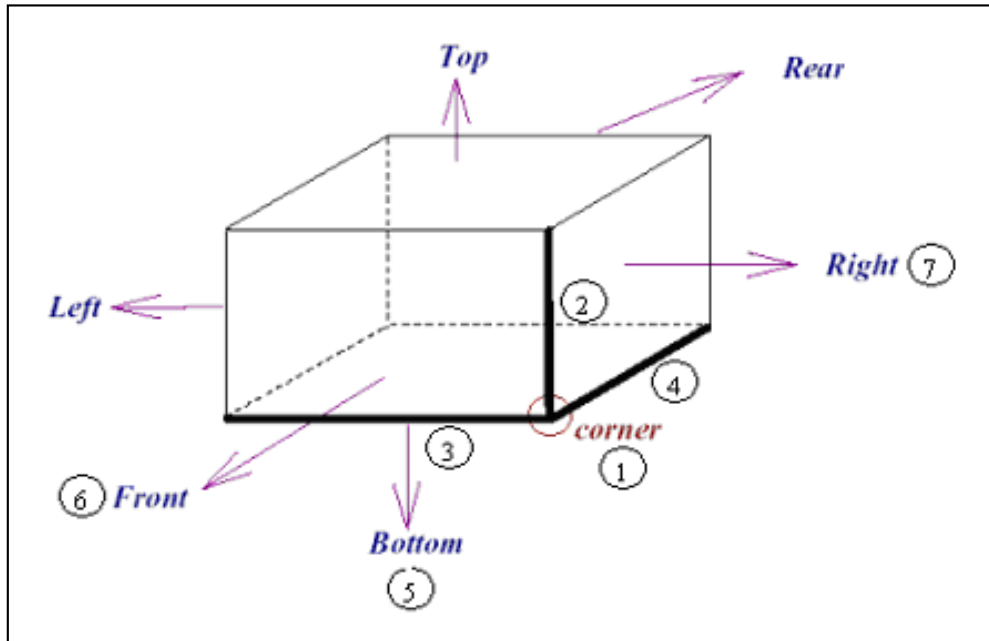





**DROP POSITION**









**DROP SEQUENCE**

<b>DROP</b>	<b>IMPACT SURFACE</b>
1	Corner (2-3-4)
2	Edge 1 (2)
3	Edge 2 (3)
4	Edge 3 (4)
5	Bottom (Flat 5)
6	Front (Flat 6)
7	Right (Flat 7)

**Attachment 2:**

Drop Sequence	Test Setup	Test Result
1		
2		
3		
4		



Drop Sequence	Test Setup	Test Result
5		
6		
7		

Open Package check for internal after drop test



## 2. UN38.3 Test Report

Test Period	2017/11/21~2017/12/06		Test Spec.	ST/SG/AC.10/11/Rev.5 Amend.1&2	
Parts Name	Battery Pack	Application	NB	Quantity	Pack 16PCS/Cell 25pcs

### 2.1 Test Summary

Item	Test Item	Test Result	Details
T1	Altitude simulation test (UN38.3-1)	Pass	Page 9
T2	Thermal test (UN38.3-2)	Pass	Page 10
T3	Vibration test (UN38.3-3)	Pass	Page 11
T4	Shock test (UN38.3-4)	Pass	Page 12
T5	Short Circuit test (UN38.3-5)	Pass	Page 13
T6	Crush Test (UN38.3-6)	Pass	Page 13
T7	Overcharge test (UN38.3-7)	Pass	Page 14
T8	Forced discharge test (UN38.3-8)	Pass	Page 15

**The battery pack passes UN38.3 test.**

**2.2 Test sample list**

No.	Pack S/N	Test item	No.	Cell Num.	Test item
1	Sample No:1/16	38.3.1~5	1	Coslight CA595490HV 4645mAh	38.3.6
2	Sample No:2/16	38.3.1~5	2	Coslight CA595490HV 4645mAh	38.3.6
3	Sample No:3/16	38.3.1~5	3	Coslight CA595490HV 4645mAh	38.3.6
4	Sample No:4/16	38.3.1~5	4	Coslight CA595490HV 4645mAh	38.3.6
5	Sample No:5/16	38.3.1~5	5	Coslight CA595490HV 4645mAh	38.3.6
6	Sample No:6/16	38.3.1~5	6	Coslight CA595490HV 4645mAh	38.3.8
7	Sample No:7/16	38.3.1~5	7	Coslight CA595490HV 4645mAh	38.3.8
8	Sample No:8/16	38.3.1~5	8	Coslight CA595490HV 4645mAh	38.3.8
9	Sample No:9/16	38.3.7	9	Coslight CA595490HV 4645mAh	38.3.8
10	Sample No:10/16	38.3.7	10	Coslight CA595490HV 4645mAh	38.3.8
11	Sample No:11/16	38.3.7	11	Coslight CA595490HV 4645mAh	38.3.8
12	Sample No:12/16	38.3.7	12	Coslight CA595490HV 4645mAh	38.3.8
13	Sample No:13/16	38.3.7	13	Coslight CA595490HV 4645mAh	38.3.8
14	Sample No:14/16	38.3.7	14	Coslight CA595490HV 4645mAh	38.3.8
15	Sample No:15/16	38.3.7	15	Coslight CA595490HV 4645mAh	38.3.8
16	Sample No:16/16	38.3.7	16	Coslight CA595490HV 4645mAh	38.3.8
			17	Coslight CA595490HV 4645mAh	38.3.8
			18	Coslight CA595490HV 4645mAh	38.3.8
			19	Coslight CA595490HV 4645mAh	38.3.8
			20	Coslight CA595490HV 4645mAh	38.3.8
			21	Coslight CA595490HV 4645mAh	38.3.8
			22	Coslight CA595490HV 4645mAh	38.3.8
			23	Coslight CA595490HV 4645mAh	38.3.8
			24	Coslight CA595490HV 4645mAh	38.3.8
			25	Coslight CA595490HV 4645mAh	38.3.8



**2.3 Test result**

Item	Test Item	Test specification	Judge criteria	Sample(s)				
T1	Altitude Simulation (UN38.3-1)	1-1. 4 batteries are standard charged. 4 batteries are 1C cycled 50 times, ending in fully charged state. All batteries weight is measured. The charged batteries voltage are measured and recorded. 1-2. Batteries shall be stored at a pressure of 11.6Kpa or less for at least six hours at ambient temperature 20+/-5 °C. 1-3. Vacuum is released. All cells weight is measured. The charged cell voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)				
Test Period	Start: 2017/11/21                      End: 2017/11/21							
Test Equipment	數位電表 Q153, 電子天平 Q090, 真空烘箱 Q146							
Major Problem	-							
Warning Point	-							
Recommendation	The battery packs pass the test.							
Raw Data	<b>Altitude Simulation Test on Charged Packs</b>							
	No.	Before		After		voltage residue	mass loss	other event
		OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
	1	12.549	217.27	12.547	217.25	99.98%	0.01%	O
	2	12.551	217.23	12.542	217.18	99.93%	0.02%	O
	3	12.539	217.28	12.538	217.26	99.99%	0.01%	O
	4	12.557	217.19	12.554	217.17	99.98%	0.01%	O
	5	12.539	217.31	12.537	217.28	99.98%	0.01%	O
	6	12.578	217.29	12.575	217.25	99.98%	0.02%	O
	7	12.547	217.26	12.546	217.23	99.99%	0.01%	O
8	12.553	217.33	12.549	217.28	99.97%	0.02%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								

Item	Test Item	Test specification	Judge criteria	Sample(s)				
T2	Thermal test (UN38.3-2)	2-1. Packs are stored for 6 hours at $72\pm 2^{\circ}\text{C}$ , followed by storage for 6 hours at $-40\pm 2^{\circ}\text{C}$ . The maximum time interval between test temperature extremes is 30 minutes. 2-2.Repeat 2-1 for 10 times. Then store the packs at ambient for 24 hours. All packs weight are measured. The charged battery voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)				
Test Period		Start: 2017/11/23                      End:2017/11/29						
Test Equipment		數位電表 Q153, 電子天平 Q090, 冷熱衝擊機 Q0446						
Major Problem		-						
Warning Point		-						
Recommendation		The packs pass the test.						
Raw Data	<b>Thermal Test on Charged Packs</b>							
	No.	Before		After		voltage residue	mass loss	other event
		OCV (V)	Weight (g)	OCV (V)	Weight (g)			
	1	12.547	217.25	12.478	217.23	99.45%	0.01%	O
	2	12.542	217.18	12.466	217.16	99.39%	0.01%	O
	3	12.538	217.26	12.463	217.23	99.40%	0.01%	O
	4	12.554	217.17	12.480	217.15	99.41%	0.01%	O
	5	12.537	217.28	12.466	217.25	99.43%	0.01%	O
	6	12.575	217.25	12.500	217.22	99.40%	0.01%	O
	7	12.546	217.23	12.478	217.20	99.46%	0.01%	O
8	12.549	217.28	12.474	217.24	99.40%	0.02%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								

Item	Test Item	Test specification	Judge criteria	Sample(s)				
T3	Vibration test (UN38.3-3)	3-1. Packs are firmly secured to the platform of the vibration machine without distorting the packs in such a manner as to faithfully transmit the vibration. The vibration shall be a sinusoidal waveform with a logarithmic sweep between 7 and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle shall be repeated 12 times for a total of 3 hours for each of 3 mutually perpendicular to the terminal face. 3-2. The logarithmic frequency sweep is as follows: 7-18 Hz → 1gn 18-50 Hz → 0.8mm amplitude 50-200 Hz → 8gn 3-3. All packs weight are measured. The charged packs voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)				
Test Period	Start: 2017/11/30 End:2017/12/01							
Test Equipment	數位電表 Q153, 電子天平 Q090, 振動測試機 Q300							
Major Problem	-							
Warning Point	-							
Recommendation	The packs pass the test.							
Raw Data	<b>Vibration Test on Charged Packs</b>							
	No.	Before		After		voltage residue	mass loss	other event
		OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
	1	12.478	217.23	12.471	217.19	99.94%	0.02%	O
	2	12.466	217.16	12.459	217.13	99.94%	0.01%	O
	3	12.463	217.23	12.455	217.19	99.94%	0.02%	O
	4	12.480	217.15	12.472	217.11	99.94%	0.02%	O
	5	12.466	217.25	12.458	217.22	99.94%	0.02%	O
	6	12.500	217.22	12.494	217.18	99.95%	0.02%	O
	7	12.478	217.20	12.469	217.17	99.93%	0.02%	O
8	12.474	217.24	12.467	217.21	99.94%	0.01%	O	
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire								
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire								

Item	Test Item	Test specification	Judge criteria	Sample(s)					
T4	Shock test (UN38.3-4)	4-1. Packs shall be secured to the testing machine by means of a rigid mount, which will support all mounting surfaces. 4-2. Packs shall be subjected to a half-sine shock of peak acceleration 150gn and pulse duration of 6 milliseconds. Each pack shall be subjected to 3 shocks in the positive direction followed by three shocks in the negative direction of three mutually perpendicularly mounting positions of the pack for a total of 18 shocks. 4-3. All batteries weight are measured. The charged cell voltage are measured and recorded.	No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)					
Test Period		Start: 2017/12/04      End:2017/12/04							
Test Equipment		數位電表 Q153, 電子天平 Q090, 衝擊測試機 Q154							
Major Problem		-							
Warning Point		-							
Recommendation		The packs pass the test.							
Raw Data		<b>Shock Test on Charged Packs</b>							
		No.	Before		After		voltage residue	mass loss	other event
			OCV (V)	Weight (g)	OCV (V)	Weight (g)	Volt (%)	Weight (%)	
		1	12.471	217.19	12.465	217.19	99.95%	0.00%	O
		2	12.459	217.13	12.454	217.12	99.96%	0.00%	O
		3	12.455	217.19	12.450	217.18	99.96%	0.00%	O
		4	12.472	217.11	12.466	217.10	99.95%	0.00%	O
		5	12.458	217.22	12.454	217.21	99.97%	0.00%	O
		6	12.494	217.18	12.487	217.17	99.94%	0.00%	O
		7	12.469	217.17	12.463	217.16	99.95%	0.00%	O
8	12.467	217.21	12.462	217.21	99.96%	0.00%	O		
Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire									
O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire									

Item	Test Item	Test specification	Judge criteria	Sample(s)
T5	Short Circuit Test (UN38.3-5)	5-1.Packs are placed in to a 55±2°C oven, and exterior packs temperature are monitored 5-2.When packs exterior reach 55±2°C, they are shorted by connecting terminals with a copper wire of resistance less than 100m Ohm. 5-4. The short was continued for more than 1hour or the cell temperature return to 55°C. The packs are observed for a further 6 hours.	No rupture, no disassembly, no explosion, no fire, no smoke. Packs exterior peak temperature <170°C.	4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8)
Test Period		Start: 2017/12/05      End:2017/12/06		
Test Equipment		數位電表 Q153, 資料收集器 Q075, 烘箱 Q171		
Recommendation		The packs pass the test.		
Raw Data		<b>Short Circuit Test on Charged Packs</b>		
		No.	Max. Temp.(°C)	Other event
		1	54.69	O
		2	55.76	O
		3	55.69	O
		4	54.26	O
5	54.19	O		
6	55.78	O		
7	54.98	O		
8	55.19	O		
Note: D-Disassembly ; R-Rupture ; F-Fire				
O- No Disassembly , No Rupture , No Fire				
Item	Test Item	Test specification	Judge criteria	Sample(s)
T6	Crush test/ Impact test (UN38.3-6)	6-1.Cell's diameter > 20mm, Execution impact test. (A 9.1 Kg mass is to be dropped from a height of 61±2.5cm onto the sample.)  6-2.Cell's diameter < 20mm, Execution crush test (The cells are crushed with a 13 KN with the crush tester. Once the force is obtained it is to be released.)	External temperature of cell does not exceed 170°C and there is no disassembly and no fire within 6 hours of the test.	5 cells are 50% charged (Cell #1~5)
Test Period		Start: 2017/11/22      End: 2017/11/22		
Test Equipment		數位電表 Q153, 資料收集器 Q152, 擠壓試驗機 Q437/撞擊測試機 Q231		
Recommendation		The Cells pass the test.		
Raw Data		<b>Crush Test on 50% Charged Cells</b>		
		No.	Max. Temp.(°C)	Other event
		1	21.36	O
		2	20.59	O
		3	21.57	O
		4	20.46	O
5	21.34	O		
Note: D-Disassembly ; F-Fire / O-No Disassembly , No Fire				

Item	Test Item	Test specification	Judge criteria	Sample(s)																																																																									
T7	Overcharge test (UN38.3-7)	7-1. The charge current shall be twice the Spec's recommended maximum continuous charge current. 7-2. The minimum voltage of the test shall be as follows: (a) When the Spec's recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage of the battery or 22V. (b) When the Spec's recommended charge voltage is more than 18V, the minimum voltage of the test shall be 1.2 times the maximum charge voltage. 7-3. Tests are to be conducted at ambient temperature. The duration of the test shall be 24 hours.	No disassembly, no fire within seven days after the test.	4 packs are fully charged (Pack#9~12) 4 packs are 50 times cycled ending in fully charged state (Pack #13~16)																																																																									
Test Period		Start: 2017/11/23                      End: 2017/11/26																																																																											
Test Equipment		數位電表 Q153, 資料收集器 Q078, 電源供應器 Q148/Q149/Q150																																																																											
Major Problem		-																																																																											
Warning Point		-																																																																											
Recommendation		The packs pass the test.																																																																											
Raw Data	<table border="1"> <thead> <tr> <th colspan="3">Forced discharge are first cycle in fully discharged</th> <th colspan="3">Forced discharge are after 50 cycles ending in fully discharged</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>6</td><td>32.69</td><td>0</td><td>16</td><td>33.59</td><td>0</td></tr> <tr><td>7</td><td>33.16</td><td>0</td><td>17</td><td>35.46</td><td>0</td></tr> <tr><td>8</td><td>32.59</td><td>0</td><td>18</td><td>34.28</td><td>0</td></tr> <tr><td>9</td><td>34.15</td><td>0</td><td>19</td><td>36.59</td><td>0</td></tr> <tr><td>10</td><td>34.69</td><td>0</td><td>20</td><td>35.48</td><td>0</td></tr> <tr><td>11</td><td>33.58</td><td>0</td><td>21</td><td>34.86</td><td>0</td></tr> <tr><td>12</td><td>34.19</td><td>0</td><td>22</td><td>35.26</td><td>0</td></tr> <tr><td>13</td><td>35.26</td><td>0</td><td>23</td><td>34.78</td><td>0</td></tr> <tr><td>14</td><td>32.59</td><td>0</td><td>24</td><td>33.59</td><td>0</td></tr> <tr><td>15</td><td>38.76</td><td>0</td><td>25</td><td>36.95</td><td>0</td></tr> </tbody> </table>					Forced discharge are first cycle in fully discharged			Forced discharge are after 50 cycles ending in fully discharged			No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event	6	32.69	0	16	33.59	0	7	33.16	0	17	35.46	0	8	32.59	0	18	34.28	0	9	34.15	0	19	36.59	0	10	34.69	0	20	35.48	0	11	33.58	0	21	34.86	0	12	34.19	0	22	35.26	0	13	35.26	0	23	34.78	0	14	32.59	0	24	33.59	0	15	38.76	0	25	36.95	0
	Forced discharge are first cycle in fully discharged			Forced discharge are after 50 cycles ending in fully discharged																																																																									
	No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event																																																																							
	6	32.69	0	16	33.59	0																																																																							
	7	33.16	0	17	35.46	0																																																																							
	8	32.59	0	18	34.28	0																																																																							
	9	34.15	0	19	36.59	0																																																																							
	10	34.69	0	20	35.48	0																																																																							
	11	33.58	0	21	34.86	0																																																																							
	12	34.19	0	22	35.26	0																																																																							
	13	35.26	0	23	34.78	0																																																																							
	14	32.59	0	24	33.59	0																																																																							
	15	38.76	0	25	36.95	0																																																																							
	Note:D-Disassembly ; F-Fire / O-No Disassembly , No Fire																																																																												



Item	Test Item	Test specification	Judge criteria	Sample(s)																																																																									
T8	Forced discharge test (UN38.3-8)	Cell shall be forced discharged at ambient temperature by connecting it in series with a 12 V D.C. power supply at an initial current equal to the maximum discharge current Specified by the manufacturer.	No disassembly, no fire within seven days after the test.	10 cells are first cycle in fully discharged states (Pack#6~15) 10 cells are after 50 cycles ending in fully discharged states (Pack #16~25)																																																																									
Test Period		Start: 2017/11/28      End:2017/12/01																																																																											
Test Equipment		數位電表 Q153, 資料收集器 Q160, 電源供應器 Q147/Q236/Q237																																																																											
Major Problem		-																																																																											
Warning Point		-																																																																											
Recommendation		The packs pass the test.																																																																											
Raw Data		<table border="1"> <thead> <tr> <th colspan="3">Forced discharge are first cycle in fully discharged</th> <th colspan="3">Forced discharge are after 50 cycles ending in fully discharged</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>6</td><td>32.98</td><td>O</td><td>16</td><td>35.69</td><td>O</td></tr> <tr><td>7</td><td>35.46</td><td>O</td><td>17</td><td>32.59</td><td>O</td></tr> <tr><td>8</td><td>35.78</td><td>O</td><td>18</td><td>34.83</td><td>O</td></tr> <tr><td>9</td><td>34.19</td><td>O</td><td>19</td><td>32.47</td><td>O</td></tr> <tr><td>10</td><td>32.16</td><td>O</td><td>20</td><td>34.67</td><td>O</td></tr> <tr><td>11</td><td>31.49</td><td>O</td><td>21</td><td>35.61</td><td>O</td></tr> <tr><td>12</td><td>33.47</td><td>O</td><td>22</td><td>34.79</td><td>O</td></tr> <tr><td>13</td><td>34.67</td><td>O</td><td>23</td><td>32.16</td><td>O</td></tr> <tr><td>14</td><td>35.61</td><td>O</td><td>24</td><td>31.49</td><td>O</td></tr> <tr><td>15</td><td>34.79</td><td>O</td><td>25</td><td>33.47</td><td>O</td></tr> </tbody> </table>				Forced discharge are first cycle in fully discharged			Forced discharge are after 50 cycles ending in fully discharged			No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event	6	32.98	O	16	35.69	O	7	35.46	O	17	32.59	O	8	35.78	O	18	34.83	O	9	34.19	O	19	32.47	O	10	32.16	O	20	34.67	O	11	31.49	O	21	35.61	O	12	33.47	O	22	34.79	O	13	34.67	O	23	32.16	O	14	35.61	O	24	31.49	O	15	34.79	O	25	33.47	O
		Forced discharge are first cycle in fully discharged			Forced discharge are after 50 cycles ending in fully discharged																																																																								
		No.	Max. Temp.(°C)	Other event	No.	Max. Temp.(°C)	Other event																																																																						
		6	32.98	O	16	35.69	O																																																																						
		7	35.46	O	17	32.59	O																																																																						
		8	35.78	O	18	34.83	O																																																																						
		9	34.19	O	19	32.47	O																																																																						
		10	32.16	O	20	34.67	O																																																																						
		11	31.49	O	21	35.61	O																																																																						
		12	33.47	O	22	34.79	O																																																																						
		13	34.67	O	23	32.16	O																																																																						
		14	35.61	O	24	31.49	O																																																																						
		15	34.79	O	25	33.47	O																																																																						
		Note:D-Disassembly ; F-Fire / O-No Disassembly , No Fire																																																																											