

Battery Pack Test Report ***(Package Drop & UN38.3)***

Customer: Lenovo

Pack Model: L17C3PG1

Nominal voltage: 11.4V

Nominal capacity: 4645mAh/52.5Wh

Configuration: 3S1P

Customer P/N: 5B10T30218

Celxpert P/N: 921300225


Cell Type: Coslight CA595490HV 4645mAh

Jan. 10. 2019

Approved by _____

Reviewed by _____

Prepared by _____

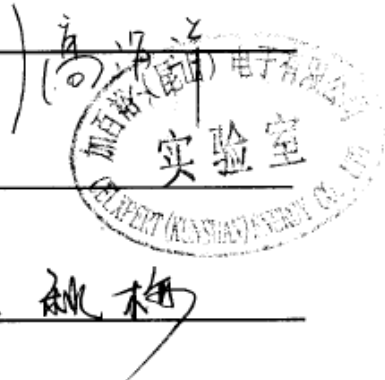

UN38.3 Lithium Battery Test Summary

| | | | |
|-------------------------------------------------|-------------------------------------------------------------------------------|--------------------------------|-------------------------------------------------------------------------------|
| Edition of UN Manual of Tests and Criteria Used | | ST/SG/AC.10/11/Rev.5 Amend.1&2 | |
| Customer | Lenovo | Sample type | Pack 16PCS/Cell 25pcs |
| Model Name | L17C3PG1 | Pack Configuration | 3S1P |
| Rating | Nominal : 4645mAh/52.5Wh Rating : 4510mAh/51Wh | Battery weight | 217g |
| Cell Factory/Model | Coslight CA595490HV 4645mAh | Physical Description | Polymer |
| Factory Address | Hi-Tech Industrial Park, 1111 Hanpu Rd, Kun Shan, Jiangsu 215316, China | Laboratory Address | Hi-Tech Industrial Park, 1111 Hanpu Rd, Kun Shan, Jiangsu 215316, China |
| Factory Name | Celxpert (kunshan) Energy,Ltd | Laboratory Name | CPK LAB |
| Factory Tel | +86-512-57775999 | Laboratory Tel | +86-512-57775999 |
| Factory E-mail | Frank_Gao@cn.celxpert.com | Lab E-mail | Frank_Gao@cn.celxpert.com |
| Factory Web | www.celxpert.com.tw | Laboratory Web | www.celxpert.com.tw |
| Client Date | 2017/11/21 | Completing Data | 2017/12/06 |
| Item | Test Item | Test Result(Pass/Fail) | |
| 38.3.4.1 T1 | Altitude simulation | Pass | |
| 38.3.4.1 T2 | Thermal | Pass | |
| 38.3.4.1 T3 | Vibration | Pass | |
| 38.3.4.1 T4 | Shock | Pass | |
| 38.3.4.1 T5 | External Short Circuit | Pass | |
| 38.3.4.1 T6 | Crush | Pass | |
| 38.3.4.1 T7 | Overcharge | Pass | |
| 38.3.4.1 T8 | Forced Discharge | Pass | |

| | | |
|-------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------|
| Approved By | Checked By | Prepared By |
|  |  |  |
| Section manager | Section manager | Engineer |



Figure photo of the pack



Lenovo

Lenovo is the trademark of Lenovo, used under license.
 Lenovo 是联想集团所属企业的商标,根据许可使用。

Model Name 型号/型號: L17C3PG1
 3ICP6/54/90

Rating : 11.4V == TYP 4645mAh/52.5Wh MIN 4510mAh/51Wh
 額定容量: 4510mAh 充電限制電壓: 13.05V

For use with Lenovo personal computer
 制造商: 加百裕工業股份有限公司

Manufactured by Celxpert(Kunshan) Energy Co.,Ltd.

PS:此報告僅針對送檢樣品有效

The test report is valid for the tested samples only.

1. Package Drop Test Report

| | | | | | |
|--------------|-----------------|-------------|------------------|----------------------|--------|
| Test Period | 2017/11/13 | | Test Spec. | IATA A58 & QS-3Q-043 | |
| Sample Level | Mass Production | Sample Mode | Finished Product | Quantity | 32 PCS |

1.1 DESCRIPTION OF TEST EQUIPMENTS

Kingdom Technology KD-128AS drop tester. Description of performance:

Payload capacity: 160 lbs. (72.6 kg)

Payload dimensions: Length: 61 cm / Width: 76 cm / Height: 90cm

Drop height range: 30 - 180 cm

Base Plate Material: Solid Steel (Std.)

Base Plate Size: 76.2x114.3x1.3cm

1.2 TEST CONDITION

Drop height: 120cm

Drop weight: 8.167kg

Drop position: One corner, three edges and three faces with 1 time. (Total: 7 drops).

Drop Position and sequence: Ref. attachment 1

1.3 SUMMARY OF TEST

Concluding the follow check items, the result of the test is **pass**.


| Check items | Before | After |
|-------------------------|--------------------------------------------------------------------------|--------------------------------------------------------------------------|
| Battery pack function | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail |
| Battery pack appearance | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail |
| Package internal status | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail |
| Package outside status | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail | <input checked="" type="checkbox"/> Normal <input type="checkbox"/> Fail |

Test photographs please refer to Attachment 2

Function Check details please refer to Attachment 3

Attachment 1:



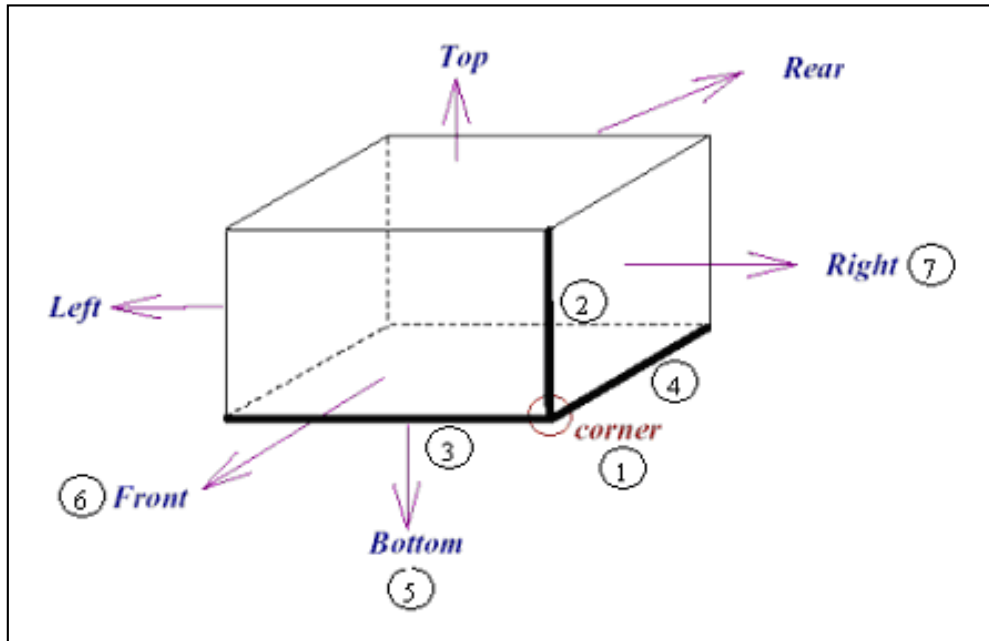





DROP POSITION









DROP SEQUENCE

| DROP | IMPACT SURFACE |
|-------------|-----------------------|
| 1 | Corner (2-3-4) |
| 2 | Edge 1 (2) |
| 3 | Edge 2 (3) |
| 4 | Edge 3 (4) |
| 5 | Bottom (Flat 5) |
| 6 | Front (Flat 6) |
| 7 | Right (Flat 7) |

Attachment 2:

| Drop Sequence | Test Setup | Test Result |
|---------------|-------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------|
| 1 |  |  |
| 2 |  |  |
| 3 |  |  |
| 4 |  |  |

| Drop Sequence | Test Setup | Test Result |
|---------------|-------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------|
| 5 |  |  |
| 6 |  |  |
| 7 |  |  |

Open Package check for internal after drop test



2. UN38.3 Test Report

| | | | | | |
|-------------|-----------------------|-------------|------------|--------------------------------|-----------------------|
| Test Period | 2017/11/21~2017/12/06 | | Test Spec. | ST/SG/AC.10/11/Rev.5 Amend.1&2 | |
| Parts Name | Battery Pack | Application | NB | Quantity | Pack 16PCS/Cell 25pcs |

2.1 Test Summary

| Item | Test Item | Test Result | Details |
|------|-------------------------------------|-------------|---------|
| T1 | Altitude simulation test (UN38.3-1) | Pass | Page 9 |
| T2 | Thermal test (UN38.3-2) | Pass | Page 10 |
| T3 | Vibration test (UN38.3-3) | Pass | Page 11 |
| T4 | Shock test (UN38.3-4) | Pass | Page 12 |
| T5 | Short Circuit test (UN38.3-5) | Pass | Page 13 |
| T6 | Crush Test (UN38.3-6) | Pass | Page 13 |
| T7 | Overcharge test (UN38.3-7) | Pass | Page 14 |
| T8 | Forced discharge test (UN38.3-8) | Pass | Page 15 |
| | | | |
| | | | |
| | | | |

The battery pack passes UN38.3 test.

2.2 Test sample list

| No. | Pack S/N | Test item | No. | Cell Num. | Test item |
|-----|-----------------|-----------|-----|-----------------------------|-----------|
| 1 | Sample No:1/16 | 38.3.1~5 | 1 | Coslight CA595490HV 4645mAh | 38.3.6 |
| 2 | Sample No:2/16 | 38.3.1~5 | 2 | Coslight CA595490HV 4645mAh | 38.3.6 |
| 3 | Sample No:3/16 | 38.3.1~5 | 3 | Coslight CA595490HV 4645mAh | 38.3.6 |
| 4 | Sample No:4/16 | 38.3.1~5 | 4 | Coslight CA595490HV 4645mAh | 38.3.6 |
| 5 | Sample No:5/16 | 38.3.1~5 | 5 | Coslight CA595490HV 4645mAh | 38.3.6 |
| 6 | Sample No:6/16 | 38.3.1~5 | 6 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 7 | Sample No:7/16 | 38.3.1~5 | 7 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 8 | Sample No:8/16 | 38.3.1~5 | 8 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 9 | Sample No:9/16 | 38.3.7 | 9 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 10 | Sample No:10/16 | 38.3.7 | 10 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 11 | Sample No:11/16 | 38.3.7 | 11 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 12 | Sample No:12/16 | 38.3.7 | 12 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 13 | Sample No:13/16 | 38.3.7 | 13 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 14 | Sample No:14/16 | 38.3.7 | 14 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 15 | Sample No:15/16 | 38.3.7 | 15 | Coslight CA595490HV 4645mAh | 38.3.8 |
| 16 | Sample No:16/16 | 38.3.7 | 16 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 17 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 18 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 19 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 20 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 21 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 22 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 23 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 24 | Coslight CA595490HV 4645mAh | 38.3.8 |
| | | | 25 | Coslight CA595490HV 4645mAh | 38.3.8 |

2.3 Test result

| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | |
|-------------------------------------------------------------------|--------------------------------------------------------|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------------------------|------------|-----------------------------|-------------------------|-------------|
| T1 | Altitude Simulation (UN38.3-1) | 1-1. 4 batteries are standard charged. 4 batteries are 1C cycled 50 times, ending in fully charged state. All batteries weight is measured. The charged batteries voltage are measured and recorded. 1-2. Batteries shall be stored at a pressure of 11.6Kpa or less for at least six hours at ambient temperature 20+/-5 °C. 1-3. Vacuum is released. All cells weight is measured. The charged cell voltage are measured and recorded. | No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%. | 4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8) | | | | |
| Test Period | Start: 2017/11/21 End: 2017/11/21 | | | | | | | |
| Test Equipment | 數位電表 Q153, 電子天平 Q090, 真空烘箱 Q146 | | | | | | | |
| Major Problem | - | | | | | | | |
| Warning Point | - | | | | | | | |
| Recommendation | The battery packs pass the test. | | | | | | | |
| Raw Data | Altitude Simulation Test on Charged Packs | | | | | | | |
| | No. | Before | | After | | voltage residue Volt (%) | mass loss Weight (%) | other event |
| | | OCV (V) | Weight (g) | OCV (V) | Weight (g) | | | |
| | 1 | 12.549 | 217.27 | 12.547 | 217.25 | 99.98% | 0.01% | O |
| | 2 | 12.551 | 217.23 | 12.542 | 217.18 | 99.93% | 0.02% | O |
| | 3 | 12.539 | 217.28 | 12.538 | 217.26 | 99.99% | 0.01% | O |
| | 4 | 12.557 | 217.19 | 12.554 | 217.17 | 99.98% | 0.01% | O |
| | 5 | 12.539 | 217.31 | 12.537 | 217.28 | 99.98% | 0.01% | O |
| | 6 | 12.578 | 217.29 | 12.575 | 217.25 | 99.98% | 0.02% | O |
| | 7 | 12.547 | 217.26 | 12.546 | 217.23 | 99.99% | 0.01% | O |
| | 8 | 12.553 | 217.33 | 12.549 | 217.28 | 99.97% | 0.02% | O |
| Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire | | | | | | | | |
| O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire | | | | | | | | |

| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | |
|-------------------------------------------------------------------|--------------------------------------|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------------------------|------------|-----------------|-----------|-------------|
| T2 | Thermal test (UN38.3-2) | 2-1. Packs are stored for 6 hours at $72\pm 2^{\circ}\text{C}$, followed by storage for 6 hours at $-40\pm 2^{\circ}\text{C}$. The maximum time interval between test temperature extremes is 30 minutes. 2-2.Repeat 2-1 for 10 times. Then store the packs at ambient for 24 hours. All packs weight are measured. The charged battery voltage are measured and recorded. | No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%. | 4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8) | | | | |
| Test Period | | Start: 2017/11/23 End:2017/11/29 | | | | | | |
| Test Equipment | | 數位電表 Q153, 電子天平 Q090, 冷熱衝擊機 Q0446 | | | | | | |
| Major Problem | | - | | | | | | |
| Warning Point | | - | | | | | | |
| Recommendation | | The packs pass the test. | | | | | | |
| Raw Data | Thermal Test on Charged Packs | | | | | | | |
| | No. | Before | | After | | voltage residue | mass loss | other event |
| | | OCV (V) | Weight (g) | OCV (V) | Weight (g) | | | |
| | 1 | 12.547 | 217.25 | 12.478 | 217.23 | 99.45% | 0.01% | O |
| | 2 | 12.542 | 217.18 | 12.466 | 217.16 | 99.39% | 0.01% | O |
| | 3 | 12.538 | 217.26 | 12.463 | 217.23 | 99.40% | 0.01% | O |
| | 4 | 12.554 | 217.17 | 12.480 | 217.15 | 99.41% | 0.01% | O |
| | 5 | 12.537 | 217.28 | 12.466 | 217.25 | 99.43% | 0.01% | O |
| | 6 | 12.575 | 217.25 | 12.500 | 217.22 | 99.40% | 0.01% | O |
| | 7 | 12.546 | 217.23 | 12.478 | 217.20 | 99.46% | 0.01% | O |
| 8 | 12.549 | 217.28 | 12.474 | 217.24 | 99.40% | 0.02% | O | |
| Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire | | | | | | | | |
| O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire | | | | | | | | |

| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | |
|-------------------------------------------------------------------|----------------------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------------------------|------------|-----------------|------------|-------------|
| T3 | Vibration test (UN38.3-3) | 3-1. Packs are firmly secured to the platform of the vibration machine without distorting the packs in such a manner as to faithfully transmit the vibration. The vibration shall be a sinusoidal waveform with a logarithmic sweep between 7 and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle shall be repeated 12 times for a total of 3 hours for each of 3 mutually perpendicular to the terminal face. 3-2. The logarithmic frequency sweep is as follows: 7-18 Hz → 1gn 18-50 Hz → 0.8mm amplitude 50-200 Hz → 8gn 3-3. All packs weight are measured. The charged packs voltage are measured and recorded. | No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%. | 4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8) | | | | |
| Test Period | Start: 2017/11/30 End:2017/12/01 | | | | | | | |
| Test Equipment | 數位電表 Q153, 電子天平 Q090, 振動測試機 Q300 | | | | | | | |
| Major Problem | - | | | | | | | |
| Warning Point | - | | | | | | | |
| Recommendation | The packs pass the test. | | | | | | | |
| Raw Data | Vibration Test on Charged Packs | | | | | | | |
| | No. | Before | | After | | voltage residue | mass loss | other event |
| | | OCV (V) | Weight (g) | OCV (V) | Weight (g) | Volt (%) | Weight (%) | |
| | 1 | 12.478 | 217.23 | 12.471 | 217.19 | 99.94% | 0.02% | O |
| | 2 | 12.466 | 217.16 | 12.459 | 217.13 | 99.94% | 0.01% | O |
| | 3 | 12.463 | 217.23 | 12.455 | 217.19 | 99.94% | 0.02% | O |
| | 4 | 12.480 | 217.15 | 12.472 | 217.11 | 99.94% | 0.02% | O |
| | 5 | 12.466 | 217.25 | 12.458 | 217.22 | 99.94% | 0.02% | O |
| | 6 | 12.500 | 217.22 | 12.494 | 217.18 | 99.95% | 0.02% | O |
| | 7 | 12.478 | 217.20 | 12.469 | 217.17 | 99.93% | 0.02% | O |
| 8 | 12.474 | 217.24 | 12.467 | 217.21 | 99.94% | 0.01% | O | |
| Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire | | | | | | | | |
| O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire | | | | | | | | |

| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | |
|-------------------------------------------------------------------|-------------------------------------------------------|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|----------------------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------------------------|------------|-----------------|------------|-------------|
| T4 | Shock test (UN38.3-4) | 4-1. Packs shall be secured to the testing machine by means of a rigid mount, which will support all mounting surfaces. 4-2. Packs shall be subjected to a half-sine shock of peak acceleration 150gn and pulse duration of 6 milliseconds. Each pack shall be subjected to 3 shocks in the positive direction followed by three shocks in the negative direction of three mutually perpendicularly mounting positions of the pack for a total of 18 shocks. 4-3. All batteries weight are measured. The charged cell voltage are measured and recorded. | No mass loss (<0.1%), no leakage, no venting, no disassembly, no rupture and no fire. Battery voltage drop < 10%. | 4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8) | | | | |
| Test Period | Start: 2017/12/04 End:2017/12/04 | | | | | | | |
| Test Equipment | 數位電表 Q153, 電子天平 Q090, 衝擊測試機 Q154 | | | | | | | |
| Major Problem | - | | | | | | | |
| Warning Point | - | | | | | | | |
| Recommendation | The packs pass the test. | | | | | | | |
| Raw Data | Shock Test on Charged Packs | | | | | | | |
| | No. | Before | | After | | voltage residue | mass loss | other event |
| | | OCV (V) | Weight (g) | OCV (V) | Weight (g) | Volt (%) | Weight (%) | |
| | 1 | 12.471 | 217.19 | 12.465 | 217.19 | 99.95% | 0.00% | O |
| | 2 | 12.459 | 217.13 | 12.454 | 217.12 | 99.96% | 0.00% | O |
| | 3 | 12.455 | 217.19 | 12.450 | 217.18 | 99.96% | 0.00% | O |
| | 4 | 12.472 | 217.11 | 12.466 | 217.10 | 99.95% | 0.00% | O |
| | 5 | 12.458 | 217.22 | 12.454 | 217.21 | 99.97% | 0.00% | O |
| | 6 | 12.494 | 217.18 | 12.487 | 217.17 | 99.94% | 0.00% | O |
| | 7 | 12.469 | 217.17 | 12.463 | 217.16 | 99.95% | 0.00% | O |
| 8 | 12.467 | 217.21 | 12.462 | 217.21 | 99.96% | 0.00% | O | |
| Note: L-Leakage ; V-Venting ; D-Disassembly ; R-Rupture ; F-Fire | | | | | | | | |
| O-No Leakage , No Venting , No Disassembly , No Rupture , No Fire | | | | | | | | |

| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
|-------------------------------------|------------------------------------|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|------------------------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------------------------|-------------------------------------|--|--|-----|----------------|-------------|---|-------|---|---|-------|---|---|-------|---|---|-------|---|---|-------|---|---|-------|---|---|-------|---|---|-------|---|
| T5 | Short Circuit Test (UN38.3-5) | 5-1.Packs are placed in to a 55±2°C oven, and exterior packs temperature are monitored 5-2.When packs exterior reach 55±2°C, they are shorted by connecting terminals with a copper wire of resistance less than 100m Ohm. 5-4. The short was continued for more than 1hour or the cell temperature return to 55°C. The packs are observed for a further 6 hours. | No rupture, no disassembly, no explosion, no fire, no smoke. Packs exterior peak temperature <170°C. | 4 packs are standard charged (Pack#1~4) 4 packs 50 cycled ending in fully charged states (Pack#5~8) | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Test Period | | Start: 2017/12/05 End:2017/12/06 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Test Equipment | | 數位電表 Q153, 資料收集器 Q075, 烘箱 Q171 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Recommendation | | The packs pass the test. | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Raw Data | | <table border="1"> <thead> <tr> <th colspan="3">Short Circuit Test on Charged Packs</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>1</td><td>54.69</td><td>O</td></tr> <tr><td>2</td><td>55.76</td><td>O</td></tr> <tr><td>3</td><td>55.69</td><td>O</td></tr> <tr><td>4</td><td>54.26</td><td>O</td></tr> <tr><td>5</td><td>54.19</td><td>O</td></tr> <tr><td>6</td><td>55.78</td><td>O</td></tr> <tr><td>7</td><td>54.98</td><td>O</td></tr> <tr><td>8</td><td>55.19</td><td>O</td></tr> </tbody> </table> <p>Note: D-Disassembly ; R-Rupture ; F-Fire O- No Disassembly , No Rupture , No Fire</p> | | | Short Circuit Test on Charged Packs | | | No. | Max. Temp.(°C) | Other event | 1 | 54.69 | O | 2 | 55.76 | O | 3 | 55.69 | O | 4 | 54.26 | O | 5 | 54.19 | O | 6 | 55.78 | O | 7 | 54.98 | O | 8 | 55.19 | O |
| Short Circuit Test on Charged Packs | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| No. | Max. Temp.(°C) | Other event | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 1 | 54.69 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 2 | 55.76 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 3 | 55.69 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 4 | 54.26 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 5 | 54.19 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 6 | 55.78 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 7 | 54.98 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 8 | 55.19 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| T6 | Crush test/ Impact test (UN38.3-6) | 6-1.Cell's diameter >18mm, Execution impact test. (A 9.1 Kg mass is to be dropped from a height of 61±2.5cm onto the sample.) 6-2.Cell's diameter <18mm, Execution crush test (The cells are crushed with a 13 KN with the crush tester. Once the force is obtained it is to be released.) | External temperature of cell does not exceed 170°C and there is no disassembly and no fire within 6 hours of the test. | 5 cells are 50% charged (Cell #1~5) | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Test Period | | Start: 2017/11/22 End: 2017/11/22 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Test Equipment | | 數位電表 Q153, 資料收集器 Q152, 擠壓試驗機 Q437/撞擊測試機 Q231 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Recommendation | | The Cells pass the test. | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Raw Data | | <table border="1"> <thead> <tr> <th colspan="3">Crush Test on 50% Charged Cells</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>1</td><td>21.36</td><td>O</td></tr> <tr><td>2</td><td>20.59</td><td>O</td></tr> <tr><td>3</td><td>21.57</td><td>O</td></tr> <tr><td>4</td><td>20.46</td><td>O</td></tr> <tr><td>5</td><td>21.34</td><td>O</td></tr> </tbody> </table> <p>Note: D-Disassembly ; F-Fire / O-No Disassembly , No Fire</p> | | | Crush Test on 50% Charged Cells | | | No. | Max. Temp.(°C) | Other event | 1 | 21.36 | O | 2 | 20.59 | O | 3 | 21.57 | O | 4 | 20.46 | O | 5 | 21.34 | O | | | | | | | | | |
| Crush Test on 50% Charged Cells | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| No. | Max. Temp.(°C) | Other event | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 1 | 21.36 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 2 | 20.59 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 3 | 21.57 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 4 | 20.46 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| 5 | 21.34 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |

| Item | Test Item | Test specification | Judge criteria | Sample(s) |
|----------------------------------------------------------|--------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------|------------------------------------------------------------------------------------------------------------------|
| T7 | Overcharge test (UN38.3-7) | 7-1. The charge current shall be twice the Spec's recommended maximum continuous charge current. 7-2. The minimum voltage of the test shall be as follows: (a) When the Spec's recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage of the battery or 22V. (b) When the Spec's recommended charge voltage is more than 18V, the minimum voltage of the test shall be 1.2 times the maximum charge voltage. 7-3. Tests are to be conducted at ambient temperature. The duration of the test shall be 24 hours. | No disassembly, no fire within seven days after the test. | 4 packs are fully charged (Pack#9~12) 4 packs are 50 times cycled ending in fully charged state (Pack #13~16) |
| Test Period | Start: 2017/11/23 End: 2017/11/26 | | | |
| Test Equipment | 數位電表 Q153, 資料收集器 Q078, 電源供應器 Q148/Q149/Q150 | | | |
| Major Problem | - | | | |
| Warning Point | - | | | |
| Recommendation | The packs pass the test. | | | |
| Raw Data | Overcharge Test on Charged Packs | | | |
| | No. | Charge Voltage(V) | Charge Current(A) | Max. Temp.(°C) |
| | 9 | 22.0 V | 9.89 | 21.03 |
| | 10 | | | 20.46 |
| | 11 | | | 21.85 |
| | 12 | | | 20.19 |
| | 13 | | | 20.47 |
| | 14 | | | 21.36 |
| | 15 | | | 21.58 |
| | 16 | | | 20.46 |
| Note: D-Disassembly ; F-Fire / O-No Disassembly ,No Fire | | | | |

| Item | Test Item | Test specification | Judge criteria | Sample(s) | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
|----------------|----------------------------------|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------------|------------------------------------------------------|-------------|--|-----------------------------------------------------------------|--|--|-----|----------------|-------------|-----|----------------|-------------|---|-------|---|----|-------|---|---|-------|---|----|-------|---|---|-------|---|----|-------|---|---|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|----|-------|---|
| T8 | Forced discharge test (UN38.3-8) | Cell shall be forced discharged at ambient temperature by connecting it in series with a 12 V D.C. power supply at an initial current equal to the maximum discharge current Specified by the manufacturer. | No disassembly, no fire within seven days after the test. | 10 cells are first cycle in fully discharged states (Pack#6~15) 10 cells are after 50 cycles ending in fully discharged states (Pack #16~25) | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Test Period | | Start: 2017/11/28 End:2017/12/01 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Test Equipment | | 數位電表 Q153, 資料收集器 Q160, 電源供應器 Q147/Q236/Q237 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Major Problem | | - | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Warning Point | | - | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Recommendation | | The packs pass the test. | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Raw Data | | <table border="1"> <thead> <tr> <th colspan="3">Forced discharge are first cycle in fully discharged</th> <th colspan="3">Forced discharge are after 50 cycles ending in fully discharged</th> </tr> <tr> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> <th>No.</th> <th>Max. Temp.(°C)</th> <th>Other event</th> </tr> </thead> <tbody> <tr><td>6</td><td>32.98</td><td>O</td><td>16</td><td>35.69</td><td>O</td></tr> <tr><td>7</td><td>35.46</td><td>O</td><td>17</td><td>32.59</td><td>O</td></tr> <tr><td>8</td><td>35.78</td><td>O</td><td>18</td><td>34.83</td><td>O</td></tr> <tr><td>9</td><td>34.19</td><td>O</td><td>19</td><td>32.47</td><td>O</td></tr> <tr><td>10</td><td>32.16</td><td>O</td><td>20</td><td>34.67</td><td>O</td></tr> <tr><td>11</td><td>31.49</td><td>O</td><td>21</td><td>35.61</td><td>O</td></tr> <tr><td>12</td><td>33.47</td><td>O</td><td>22</td><td>34.79</td><td>O</td></tr> <tr><td>13</td><td>34.67</td><td>O</td><td>23</td><td>32.16</td><td>O</td></tr> <tr><td>14</td><td>35.61</td><td>O</td><td>24</td><td>31.49</td><td>O</td></tr> <tr><td>15</td><td>34.79</td><td>O</td><td>25</td><td>33.47</td><td>O</td></tr> </tbody> </table> | | | | Forced discharge are first cycle in fully discharged | | | Forced discharge are after 50 cycles ending in fully discharged | | | No. | Max. Temp.(°C) | Other event | No. | Max. Temp.(°C) | Other event | 6 | 32.98 | O | 16 | 35.69 | O | 7 | 35.46 | O | 17 | 32.59 | O | 8 | 35.78 | O | 18 | 34.83 | O | 9 | 34.19 | O | 19 | 32.47 | O | 10 | 32.16 | O | 20 | 34.67 | O | 11 | 31.49 | O | 21 | 35.61 | O | 12 | 33.47 | O | 22 | 34.79 | O | 13 | 34.67 | O | 23 | 32.16 | O | 14 | 35.61 | O | 24 | 31.49 | O | 15 | 34.79 | O | 25 | 33.47 | O |
| | | Forced discharge are first cycle in fully discharged | | | Forced discharge are after 50 cycles ending in fully discharged | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | No. | Max. Temp.(°C) | Other event | No. | Max. Temp.(°C) | Other event | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 6 | 32.98 | O | 16 | 35.69 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 7 | 35.46 | O | 17 | 32.59 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 8 | 35.78 | O | 18 | 34.83 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 9 | 34.19 | O | 19 | 32.47 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 10 | 32.16 | O | 20 | 34.67 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 11 | 31.49 | O | 21 | 35.61 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 12 | 33.47 | O | 22 | 34.79 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 13 | 34.67 | O | 23 | 32.16 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 14 | 35.61 | O | 24 | 31.49 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | 15 | 34.79 | O | 25 | 33.47 | O | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| | | Note:D-Disassembly ; F-Fire / O-No Disassembly , No Fire | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |